

CHLORINE DIOXIDE – RECENT CORROSION STUDIES

Overview

With the success of ClO₂ use in upstream water treatment, a few companies have raised concerns about the potential impact of ClO₂ corrosion on frac equipment. Several recently published studies, as are described below, should help reduce these concerns.

Studies

In one study¹, N80 carbon steel coupons exposed to 15% inhibited HCl for 5 minutes and subsequently to 50,000 ppm sodium chloride brine with 1-5 ppm ClO₂ for 1.5 hour, simulating a frac stage duration, showed no significant difference in corrosion rate compared to control samples without ClO₂ present. Corrosion was dominated by the presence of inhibited HCl and brine.

In another study², the corrosion rate of N80 steel coupons exposed to 7.5% HCl made from either deionized water or produced water each containing ~5 to 40 ppm ClO₂ residual and 2.5 gpt corrosion inhibitor did not show a statistically significant difference in corrosion rate from the baseline comparison with no ClO₂ present. Inhibited tests however did show a statistically significant difference from baseline uninhibited tests. As expected, ClO₂ was shown to regenerate from residual chlorite ion in produced water used in making 7.5% HCl by dilution of more concentrated acid. However, even these higher concentrations did not impact the corrosion rate of the inhibited acid.

In a third instrumental based pilot scale study³, which simulated actual conditions used in a slick water frac stage (i.e. velocity, temperature, duration, fluid additives, proppants, in fresh and in produced water, with and without ClO₂ present) a variety of carbon and stainless steel alloys used in high pressure fracturing showed no statistically significant detrimental impact of maintaining 1 to 5 ppm ClO₂ residual in the fluids as shown in Figure 1 and Table 1. However, the study showed the general corrosive, erosive nature of the frac operations. It was found that corrosion rates were extremely

high during the inhibited acid phase of each stage. The corrosion performance of carbon steel in fresh water started out poor³. The addition of ClO₂ had minimal impact. However, the presence of brine increased the corrosion rate by more than 30–40 %. Corrosion increased at pH 5.8 or below and decreased above pH 6. While it is known that O₂ levels have significant impact on corrosion rate, the presence of ClO₂ did not increase O₂ levels. The corrosion rate of stainless steel alloys was consistently good even in the presence of ClO₂. Pitting corrosion was not detected over the course of this study.

Conclusion

It can be concluded from these studies that acidic solutions are the main contributor to corrosion in frac systems followed by salt from produced water. Frac iron systems just like salt water systems experience wet dry cycles that allow concentration of salts to significantly increase general corrosion and pitting⁵. Proper use of inhibitors can minimize corrosion but not eliminate it⁶. ClO₂ when properly generated and used at typical 1-5 ppm residual concentrations for disinfection of frac water is found to have minimal impact on the corrosive erosive nature of fracturing operations.

Figure 1 Coupon Average Corrosion Rate in 60/40 Blend Fluid ³

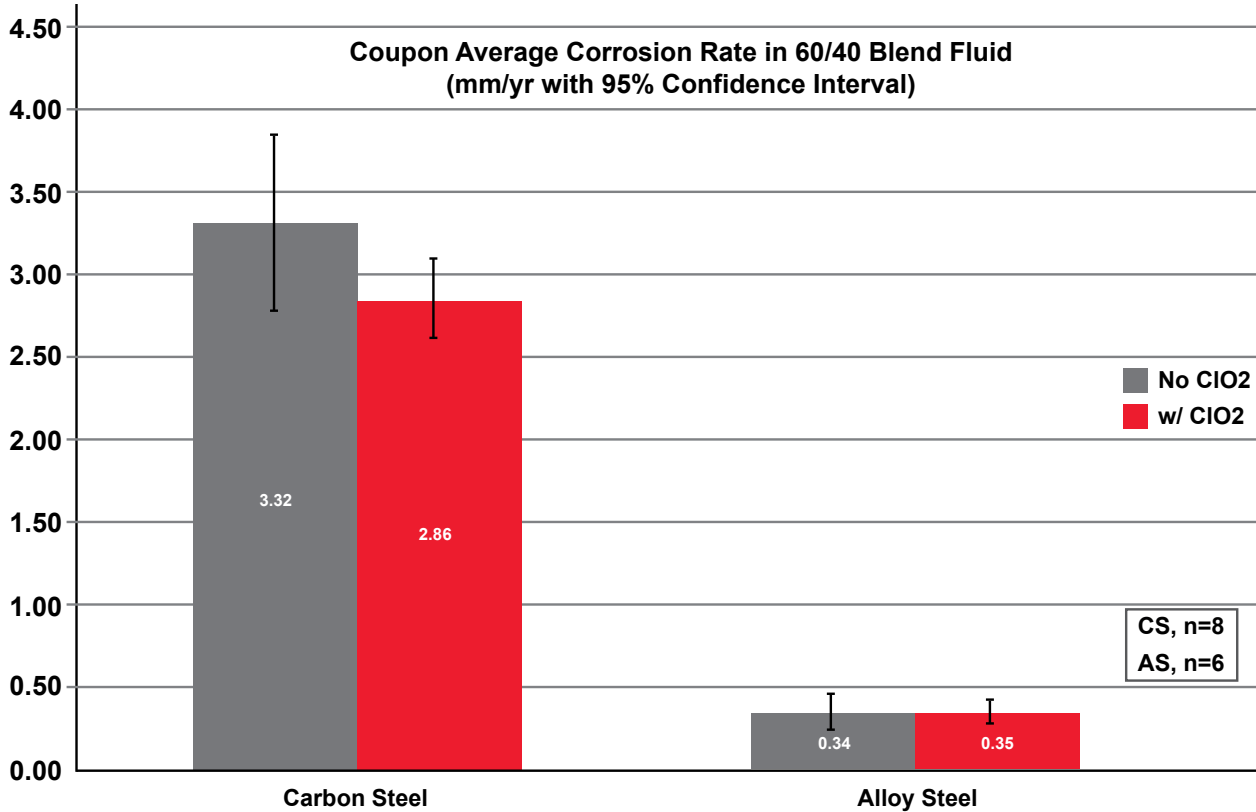


Table 1 Coupons Corrosion Rate (mm/yr) t-Test Statistical Analysis ³

Corrosion Coupon 60/40 Blend Statistical Analysis t-Test: Two-Sample Assuming Unequal Variances Comparison of 60/40 Blend Mean Corrosion Rate on CARBON STEEL			Corrosion Coupon 60/40 Blend Statistical Analysis t-Test: Two-Sample Assuming Unequal Variances Comparison of 60/40 Blend Mean Corrosion Rate on ALLOY STEEL		
	No ClO2	With ClO2		No ClO2	With ClO2
Mean	3.32	2.86	Mean	0.34	0.35
Variance	0.62	0.13	Variance	0.02	0.01
Observations	8	8	Observations	6	6
Hypothesized Mean Difference	0.00		Hypothesized Mean Difference	0	
df	10.0		df	9	
tStat	1.49		tStat	-0.017	
P(T<=t) one-tail	0.08		P(T<=t) one-tail	0.493	
t Critical one-tail	1.81		t Critical one-tail	1.833	
P(T<=t) two-tail	0.17		P(T<=t) two-tail	0.986	
t Critical two-tail	2.23		t Critical two-tail	2.262	
SD	0.7858	0.3636	SD	0.1361	0.0939
CI (.05, SD, n=8)	0.6570	0.3039	CI (.05, SD, n=8)	0.1428	0.0985
Upper	3.9750	3.1652	Upper	0.4868	0.4437
Lower	2.6610	2.5573	Lower	0.2012	0.2467

References

- ¹ "ClO₂ Disinfection- No Significant Corrosion Impact in Fracturing", White Paper. Baker Hughes, 2018.
- ² "ClO₂ Disinfection – No Significant Corrosion Impact in Acid Phase of Fracturing", Technical Bulletin E-00012. International Dioxide Inc., 02-20-18.
- ³ Monroe, Stephen. "Corrosivity of Chlorine Dioxide on Typical Oilfield Iron". Produced Water Society Seminar 2018, 13 February 2018, Marriott Sugar Land Town Center, Sugar Land, TX, Conference Presentation.
- ⁴ Fontana, Mars G. (1986) Corrosion Engineering. McGraw-Hill Book Co., NY, ISBN: 0-07-021463-8, Corrosion Ranges.
- ⁵ Fontana, Mars G. (1986) Corrosion Engineering. McGraw-Hill Book Co., NY, ISBN: 0-07-021463-8, Fig. 8-1 Corrosion of Ordinary Steel in the Sea.
- ⁶ Prues, W.et al., "Chemical Mitigation of Corrosion by Chlorine Dioxide in Oilfield Waterfloods." Material Performance, Vol 24, No.5, pp 45-50 (May 1985).
- ⁷ "Chlorine Dioxide in Fracturing Water Disinfection - Effectiveness Brings Competitive Scrutiny", White Paper L-0002 Rev 1. International Dioxide Inc., 11-30-16.
- ⁸ "Erroneous Claims from Competitors in the Market", White Paper L-0001 Rev 1. International Dioxide Inc., 11-30-16.

Health and Safety Information: Appropriate literature has been assembled which provides information concerning the health and safety precautions that must be observed when handling the International Dioxide, Inc. products mentioned in this publication. For materials mentioned which are not International Dioxide, Inc. products, appropriate industrial hygiene and other safety precautions recommended by their manufacturers should be followed. Before working with any of these products, you must read and become familiar with the available information on their hazards, proper use, and handling. This cannot be overemphasized. Information is available in several forms, e.g., safety data sheets and product labels. Consult your International Dioxide representative or contact the International Dioxide, Inc. Regulatory Affairs Representative.

The manner in which you use and the purpose to which you put and utilize our products, technical assistance and information (whether verbal, written or by way of production evaluations), including any suggested formulations and recommendations are beyond our control. Therefore, it is imperative that you test our products, technical assistance and information to determine to your own satisfaction whether they are suitable for your intended uses and applications. This application-specific analysis must at least include testing to determine suitability from a technical as well as health, safety, and environmental standpoint. Such testing has not necessarily been done by us. Unless we otherwise agree in writing, all products are sold strictly pursuant to the terms of our standard conditions of sale. All information and technical assistance is given without warranty or guarantee and is subject to change without notice. It is expressly understood and agreed that you assume and hereby expressly release us from all liability, in tort, contract or otherwise, incurred in connection with the use of our products, technical assistance, and information. Any statement or recommendation not contained herein is unauthorized and shall not bind us. Nothing herein shall be construed as a recommendation to use any product in conflict with patents covering any material or its use. No license is implied or in fact granted under the claims of any patent.

ADOX™ and any associated logos are trademarks or copyrights of International Dioxide, Inc., International Dioxide and the International Dioxide logo are trademarks of International Dioxide, Inc. All trademarks are effective in many countries worldwide.

Note: The information contained in this publication is current as of May, 2018. Please contact International Dioxide, Inc. to determine if this publication has been revised.



International Dioxide

A division of ERCO Worldwide

International Dioxide

40 Whitecap Drive
North Kingstown, RI 02852
1-800-477-6071

idiclo2.com

© 2018 International Dioxide, Inc.

E-00013